



# Green Synthesis and Antibacterial activity of Silver Nanoparticles using *Oryza Sativa* Husk Extract

Reenal M and Iruthaya Kalai Selvam S

PG and Research Centre of Zoology, Jayaraj Annapackiam College for Women (Autonomous) Periyakulam, Theni, Tamil Nadu, INDIA

Available online at: [www.isca.in](http://www.isca.in), [www.isca.me](http://www.isca.me)

Received 21<sup>st</sup> February 2015, revised 14<sup>th</sup> March 2015, accepted 16<sup>th</sup> April 2015

## Abstract

Green synthesis of nanoparticles is an important and beneficial way of controlling pathogens infection in humans without side effects caused by synthetic antibiotic and chemicals. Hence the present study is focused on the synthesis of silver nanoparticles using *Oryza sativa* husk extract. The formation of husk extract based nanoparticles was confirmed at 485nm by UV-spectral analysis and its antibacterial activity was evaluated against two harmful human pathogens *Pseudomonas aeruginosa* and *Staphylococcus aureus*. The best inhibition zone was observed in *Pseudomonas aeruginosa* than *Staphylococcus aureus*. The maximum zone was obtained in positive control Amikacin.

**Keywords:** Green synthesis, nanoparticles, antibacterial activity, UV -spectral analysis.

## Introduction

Nanoparticles have been widely applied in the fields of investigation and regulation of cellular stage, drug delivery and diagnostic imaging of cancer detection, artificial implants, tissue engineering, HIV inhibition, sensing, artificial implants, tissue engineering, photonics, optoelectronics, biological tagging, environmental pollution control, material chemistry, and water filtration using nanotechnology<sup>1-3</sup>. Human beings are infected because of multiple antibiotic resistant microorganisms such as bacteria, molds, yeast, virus, etc. This research is focused on developing new and cost effective antimicrobial agents to control antibiotic resistant microorganisms using silver based antiseptics that possess broad spectrum antimicrobial activity and considerably decreasing the susceptibility to induce microbial resistance than the synthesized chemical antibiotics<sup>4,5</sup>.

Green synthesis of silver nanoparticle is an eco- friendly method for avoiding harmful effect in medical application of silver nanoparticles synthesized by physical, chemical, photochemical such as reverse micelles, thermal decomposition of silver compounds, and radiation assisted process.

Bio activity of DNA conjugated metal nanoparticles and their application in detecting, manipulating and delivering genes has been observed<sup>6,7</sup>. Because of extraordinary chemical, physical and antimicrobial properties of silver the nano silver particles are used as a biocidal agents<sup>8,9</sup>. For example microbial infection of burn wound has been controlled using sputtered nano crystalline silver wound dressings<sup>10,11</sup>. Bactericidal effect of Ag- NPs on E- coli is due to reaction of Ag- NPs with cell wall and cytoplasmic membrane<sup>12</sup>. Ag-NPs antimicrobial activity investigation have increased due to highest bacterial resistance

## Material and Methods

of silver ion, silver compounds Ag-NPs against microbes, virus<sup>13-16</sup> and classic antibiotics<sup>17</sup>.

Medicinal plants such as *Basellaalba*, *Helianthus annuus*, *Saccharum officinarum*, *Oryza sativa*, *Sorghum bicolor*, *Zea mays*<sup>18</sup>, *Aloe vera*<sup>19</sup>, *Medicago sativa* (Alfalfa)<sup>20</sup>, *Capsicum annum*<sup>17</sup>, *Magnolia kobus*<sup>21</sup>, *Cinnamomum camphora* leaf<sup>22</sup>, *Geranium Sp*<sup>23</sup>, *Azadirachta indica* (Neam)<sup>24</sup>, *Emblca officinalis* (Amla, Indian Gooseberry)<sup>25</sup>, methanolic extract of *Eucalyptus hybrida* leaves<sup>26</sup>, *Vitex negundo* L. leaf water extract with heat treatment<sup>27</sup> and microorganism have been used in synthesis of Ag-NPs for pharmaceutical and biological application. Potent natural antioxidants such as phenolic compounds and flavonoids have been reported in *Vitex negundo*<sup>28,29</sup>.

During the milling process the outermost layer of the paddy grain is separated from the rice grains is called rice husk (or hull). Around 20% of paddy weight is husk. In Asia about 770 million tons of husk was produced annually and often burned in open or dumped on landfills as a waste<sup>30</sup> (IRRI). Disposing of husk in huge amount is causing atmospheric and water pollution. Similar to the chemical composition of many common organic fibers, the husk contains 40-50 percent of cellulose, 15-20 percent of ash, 25-30 percent lignin, and moisture 8- 15 percent<sup>31</sup>. Hence synthesis of nanoparticles from paddy husk is an effective way of utilization of the waste husk in proper way and to reduce the environmental pollution. In the present study, green synthesis of Ag-NPs using *Oryza sativa* husk extract as reducing agent and stabilizer and silver nitrate as silver precursor is attempted. The antibacterial activity of *Oryza sativa* husk extract Ag-NPs against *Pseudomonas aeruginosa* and *Staphylococcus aureus* was evaluated.

## Synthesis of silver nanoparticles from *oryza sativa* husk

**extract:** Preparation of husk extract<sup>32,33</sup>. The AR grade silver nitrate ( $\text{AgNO}_3$ ) was purchased from J.A. College at Periyakulam in Theni (Dt) and fresh *Oryza sativa* husk were collected from surroundings of Periyakulam. The *Oryza sativa* husk extract used for the reduction of  $\text{Ag}^+$  ions to  $\text{Ag}^0$  was prepared by taking 20g of thoroughly washed husk in 500 ml Erlenmeyer flask along with 100 ml of distilled water and then boiling the mixture for 5 min. then decanting it. Further, the extract was filtered with Whatman No. 1 filter paper and stored at 4°C and used for further experiments.

The husk extract (5 ml) was added to 90 ml of 1 mM  $\text{AgNO}_3$  aqueous solution and kept at room temperature for 7 hours. The bioreduced aqueous component was used to measuring UV-Vis spectra of the solution. The particle suspension was diluted 10 times with distilled water to avoid the errors due to high optical density of the solution. The reduction of pure  $\text{Ag}^{++}$  ion monitored by the absorption maxima was scanned by UV-Spectral photometer at the wave length of 200- 800nm.

**Antibacterials Test-Disc Diffusion Method<sup>34</sup>:** The antibacterial assays against *Pseudomonas aeruginosa* and *Staphylococcus aureus* were also performed by standard disc diffusion method. Nutrient agar (1g beef extract, 1g peptone, 0.5 g NaCl dissolved in 100 ml of double distilled water) was used to cultivate bacteria. The media was autoclaved and cooled. The media was poured in the petri discs and kept for 30 minutes for solidification. After 30 minutes the fresh overnight cultures of inoculums (100 µl) of two different cultures were spread on to solidified nutrient agar plates. Sterile paper discs made of Whatman filter paper, 5 mm diameter (dipped in 50 mg/ liter silver nanoparticles) along with a standard antibiotic containing

disc were placed in each plate. The cultured agar plates were incubated at 37°C for 24 h. After 24 h of incubation the zone of inhibition was investigated.

## Results and Discussion

The color changes was observed from pale white to yellowish brown color after 7 hours of incubation of rice husk extract and 1mM  $\text{AgNO}_3$  aqueous solution mixture at room temperature due to the reduction of silver ions. This exhibited the formation of silver nanoparticles (figure-2). In this experiment the silver- ion and *Oryza sativa* husk extract interaction was confirmed. Aqueous silver ions when mixed with *Oryza sativa* husk extract were reduced in solution. The husk extracts were pale white in color before adding of Ag ions and this change to yellowish brown color after 7 hours of incubation indicated the formation of silver nanoparticles. (figure-2) Due to excitation of surface plasmon vibration in silver nanoparticles produced yellowish – brown colour in aqueous solution<sup>23,24,35,36</sup>. This formation indicates that silver ions in reaction medium have been converted to elemental silver having the size of nanometric range. There is always an essential need for reducing entities in the reaction medium to bring such conversions. To ensure the presence of reducing entities in the reaction medium, reducing assay was carried out. It showed in the photographs of sample solutions containing silver nanoparticles and silver nitrate in the presence of optimized amounts of *Oryza sativa* extract solutions after completion of the reaction (figure-2). Silver nitrate reduced the *Oryza sativa* husk extract and produced the silver hydrosol because Ag ions possessed good conductivity, catalytic and chemical stability, hence it was used as a reducing agent<sup>37</sup>.

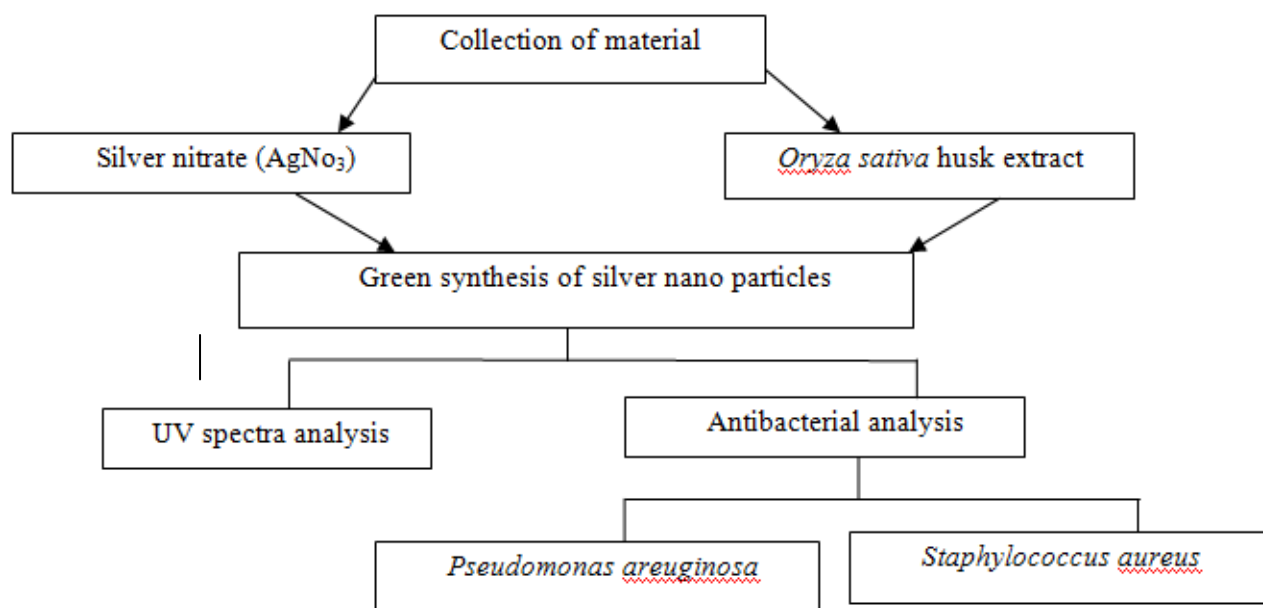


Figure-1  
Experimental Design

Absorption spectrum at different wave lengths ranging from 200-800nm exhibited a peak at around 485nm. (figure- 3). This

confirmed the formation of *Oriza sativa* husk nanoparticles. Similar phenomenon was demonstrated by the UV visible spectroscopy of the synthesized nano particles were in the range of 425- 519 nm. Out of 18 medicinal plants 15 were showed to synthesize the silver nano particles by the indication of suitable UV visible spectrum. The nanometer of various synthesized nano particles are Jeeragam- 466 nm, Kudagalari – 455 nm, Dhaniya – 432 nm, Karpokarasi- 429.8 nm, Devadaru- 429.2 nm, Gugulu- 428 nm, Cherrupunneri- 425.2 nm, Athimadhuram- 437.8 nm, Veppampattai- 439.8 nm, Vasambu-425 nm, Mahali- 444.6 nm, Pavu- 467.8 nm, Koduveli- 519.6 nm, Vettiver- 501 nm, Vilangam- 459 nm and chemical nano silver- 462 nm as a control. Shiva Shankar, *et al*<sup>38</sup> reported the faster bio- reducing methods to produce silver nanoparticle within an hour of reaction.

In our study, the AgNPs synthesized using *Oryza sativa* extract exhibited the antibacterial against two pathogens *Pseudomonas aeruginosa* and *Staphylococcus aureus*. The best inhibition zone (9mm) was observed in *Pseudomonas aeruginosa* than *Staphylococcus aureus* (6.2mm). The standard antibiotics Amikacin showed maximum zone of inhibition 15mm as compared to the nanoparticles treated discs and control (Silver nitrate) (table-1, figure-4 and 5). Silver nanoparticle has inhibitory and bactericidal effect hence it is used as antibacterial agents. They are highly toxic and hazardous to many microorganisms. Green synthesis silver based antiseptics that possesses broad spectrum antimicrobial activity and considerably decrease the susceptibility to induce microbial resistant than synthesized chemical antibiotics<sup>4,5</sup>. Coupling of inherent property of *Oryza sativa* extract with that of silver nanoparticles has really proved to be beneficial to minimize the dose that needs to be administered for total microbial reduction. Prabhu, *et al*<sup>28</sup> obtained the maximum inhibition at 150µl of plant leaf nanoparticle against *Staphylococcus aureus* using *Ocimum sanctum* and *Vitex negundo*. Pathogenic fungi namely *Candida albicans*, *C. kefy*r and *A. niger* effectively suppressed by *Euphorbia hirta* nanoparticles<sup>39</sup>.

### Conclusion

The present study confirmed that the green synthesis of nanoparticles from *oriza sativa* husk extract possesses antibacterial effect against human pathogens and suggest that it can be used to formulate new ecofriendly formulation of antibacterial agents for the treatment of bacterial infections in human beings for avoiding side effects caused by synthetic and semi synthetic chemical formulations and also proved that this is the better way of utilization of waste dumped *Oriza sativa* husk and reduce the environmental pollution to a significant extent.



Figure-2  
*Oryza sativa* extract before adding of AgNO<sub>3</sub> and The colour changes of plant extract after 6 hrs of incubation with AgNO<sub>3</sub>

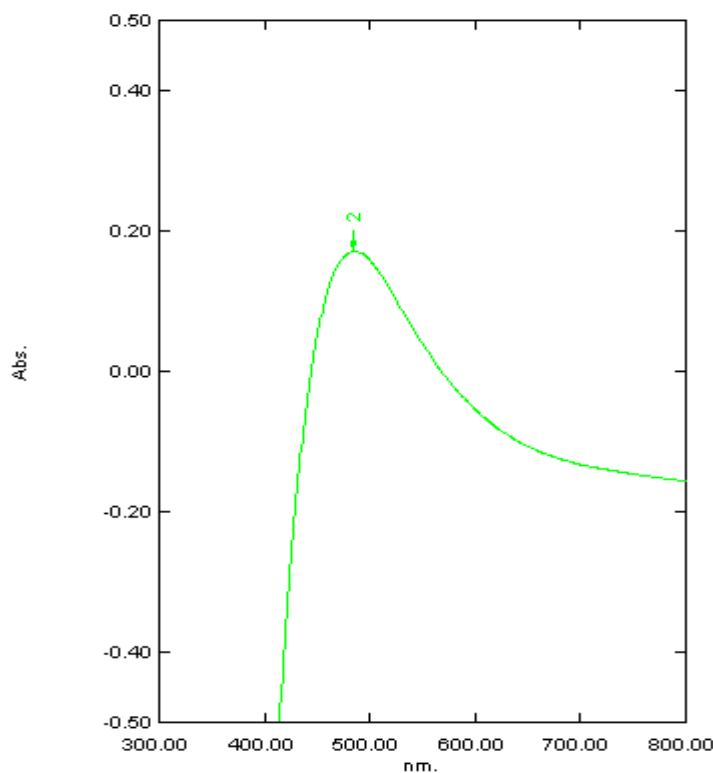


Figure-3  
The UV spectrum of *Oryza sativa* silver nanoparticles recorded at room temperature

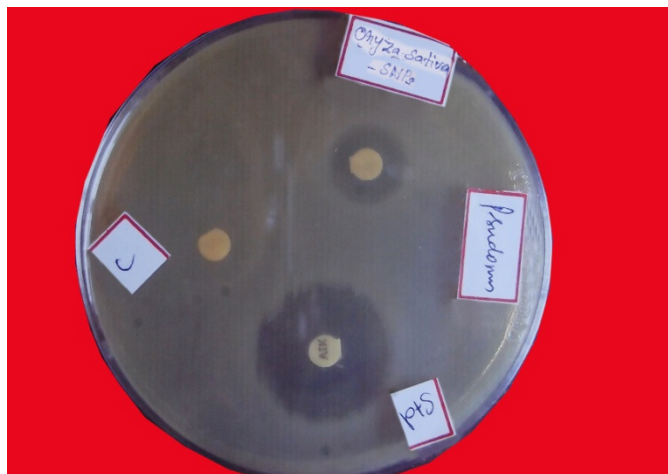


Figure-4

**Antibacterial activity of *Oryza sativa* silver nanoparticles against *Pseudomonas aeruginosa* (Gram negative)**

C: Control (silver nitrate), Std: Standard antibiotic (Amikacin), Sample: Silver nanoparticles of *Oryza sativa* husk extract, Pathogen: *Pseudomonas aeruginosa* (Gram negative)



Figure-5

**Antibacterial activity of *Oryza sativa* silver nanoparticles against *Staphylococcus aureus* (Gram positive)**

C: Control (silver nitrate), Std: Standard antibiotic (Amikacin), Sample: Silver nanoparticles of *Oryza sativa* husk extract, Pathogen: *Staphylococcus aureus* (Gram positive)

Table-1

**Antibacterial activity of *Oryza sativa* silver nanoparticles against two pathogens**

Name of the organism	Zone of inhibition (diameter)
<i>Pseudomonas aeruginosa</i>	9
<i>Staphylococcus aureus</i>	6.2

**References**

1. Gittins D.I, Bethell D, Schiffrin D.J. and Nichols R.J., A nanometre-scale electronic switch consisting of a metal

cluster and redox-addressable groups. *Nature.*, **408(6808)**, 67-69 (2000)

2. Darroudi M, Ahmad M.B, Abdullah A.H. and Ibrahim N.A., Green synthesis and characterization of gelatin-based and sugar-reduced silver nanoparticles, *Int J Nanomedicine.*, **65**, 69-574 (2011)

3. Wise K. and Brasuel M., The current state of engineered nanomaterials in consumer goods and waste streams: the need to develop nano property quantifiable sensors for monitoring engineered nanomaterials, *Nanotechnol Sci Appl.*, **4**, 73-86 (2011)

4. Jones S.A, Bowler P.G, Walker M. and Parsons D., Controlling wound bioburden with a novel silver-containing Hydrofiber dressing, *Wound Repair Regen.*, **12**, 288- 294 (2004)

5. Berger T.J, Spadaro J.A, Chapin S.E. and Becker R.O., Electrically generated silver ions: quantitative effects on bacterial and mammalian cells, *Antimicrob, Agents Ch.*, **9**, 357- 358 (1996)

6. Sonnichsen C, Reinhardt B.M, Liphardt J and Alivisatos A.P., *Nat Biotechnol.*, **23**, 741-745 (2005)

7. Rosi N.L, Giljohann D.A, Thaxton C.S, Lytton- Jean A.K, Han M.S. and Mirkin C.A., *Science*, **312**, 102-103 (2006)

8. Olson M.E, Wright J.B, Lam K and Burrell R.E., *Eur. J. Surg.*, **166**, 486- 489 (2000)

9. Lee D, Cohen R.E. and Rubner M.F., *Langmuir.*, **21**, 9651-9659 (2005)

10. Aymonier C, Schlotterbeck U, Antonietti L, Zacharias P, Thomann R, Tiller J.C. and Mecking S., *Chem Commun*, 3018-3019 (2002)

11. Tian J, Wong K.K, Ho C.M, Lok C.N, Yu W.Y, Che C.M, Chiu J.F. and Tam P.K., *Chem. Med. Chem.*, **2**, 129-136534, *J. Biol Inorg Chem.*, **12**, 527-534 (2007)

12. Chamakura K, Perez- Balleatero R, Luo Z.P, Bashir S and Liu J., comparison of bactericidal activities of silver nanoparticles with common chemical disinfectants, *Colloids surf. B.*, **84**, 88- 96 (2011)

13. Shrivastava S, Bera T, Roy A, Singh G, Ramachandrarao P and Dash D., Characterization of enhanced antibacterial effects of novel silver nanoparticles, *Nanotechnology.*, **18**, 9 (2007)

14. Magana S.M, Quintana P, Aguilar D.H, Toledo J.A, Angeles- Chavez C, Cortes M.A, Leon L, Freile- Pelegrin Y, Lopez T and Torres sanchez R.M., Antibacterial activity of montmorillonites modified with silver, *J. mol. catal. A Chem.*, **281**, 192-199 (2008)

15. Nithya R and Ragunathan R., synthesis of silver nanoparticles using *Pleurotus sajor caju* and its antimicrobial study, *Dig. J. Nanometer. Biostruct.*, **4**,

- 623- 629 (2009)
16. Lara H.H, Nunez N.V.A, Turrent L.I. and Rodriguez-Padilla C., Mode of antiviral action of silver nanoparticles against HIV- 1, *J. nanobiotechnol.*, **8**, 1- 10 (2010)
  17. Li S, Shen Y, Xie A, Yu X, Qiu L, Zhang L and Zhang Q., Green synthesis of silver nanoparticles using *Capsicum annuum* L. extract, *Green Chem.*, **9**, 852- 858 (2007)
  18. Leela A and Vivekanandam M., Tapping the unexploited plant resources for the synthesis of silver nanoparticles, *Afr. J. Biotechnol.*, **7**, 3162- 3165 (2008)
  19. Chandran S.P, Chaudhary M, Pasricha R, Ahmad A and Sastry M., Synthesis of gold nanotriangles and silver nanoparticles using *Aloe vera* plant extract, *Biotechnol. Prog.*, **22**, 577- 583 (2006)
  20. Gardea- Torresdey J.L, Gomez E, Peralta- Videa J.R, Parsons J.G, Troiani H and Jose- Yacaman M., Alfalfa sprouts: A natural source for the synthesis of silver nanoparticles, *Langmuir.*, **19**, 1357-1361(2003)
  21. Song J.Y, Jang H.K and Kim B.S., Biological synthesis of gold nanoparticles using *Magnolia kobus* and *Diopyros kaki* leaf extracts, *Process Biochem.*, **44**, 1133- 1138 (2009)
  22. Haung J, Li Q, Sun D, Lu Y, Su y, Yang X, Wang H, Wang Y, Shao W, He N, Hong J and Chen C., Biosynthesis of silver and gold nanoparticles by novel sundried *Cinnamomum comphora* leaf, *Nanotechnology.*, **18**, 105104- 105115 (2007)
  23. Shankar S.S, Rai A, Ahmad A and Sastry M., Biosynthesis of silver and gold nanoparticles from extracts of different parts of the geranium plant, *Appl. Nano Sci.*, **1**, 69- 77 (2004)
  24. Shankar S.S, Rai A, Ahmad A and Sastry M., Rapid synthesis of Au, Ag and bimetallic Au core Ag shell nanoparticles using Neem (*Azadirachta indica*) leaf broth, *J. Colloid Interface Science.*, **275**, 496-502 (2004)
  25. Amkamwar B, Damle C, Ahmed A and Sastry M., Biosynthesis of gold and silver nanoparticles using *Emblca officinalis* fruit extract, their phase transfer and transmetallation in an organic solution, *J. Nanosci. Nanotechnol.*, **5**(10), 1665- 1671 (2005)
  26. Dubey M, Bhadauria S and Kushwah B.S., Green synthesis of nanosilver particles from extract of *Eucalyptus Hybrida* (Safeda) leaf, *Dig. J. Nanomater. Biostruct.*, **4**, 537- 543 (2009)
  27. Prabhu N, Raj D.T, Yamuna G.K. and Siddiqua S.A, Innocent J.P., Synthesis of siver phyto nanoparticles and their anti-bacterial efficacy, *Dig. J. Nanomater. Biostruct.*, **5**, 185- 189 (2010)
  28. Mustafa R.A, Abdul Hamid A, Mohamad S and Abu Bakar F., Total phenolic compounds, flavonoids and radical scavenging activity of selected tropical plants, *J. Food Sci.*, **75**, C28- C35 (2010)
  29. Ling T.J, Ling W.W, Chen Y.J, Wan X.C, Xia T, Du X.X. and Zhang Z.Z., Antiseptic activity and phenolic constituents of the aerial parts of *Vitex negundo* var. *cannabifolia*, *Molecules.*, **15**, 8469- 8477 (2010)
  30. The International Rice Research Institute.(Web source), (2014)
  31. Hwang C.L and Chandra S., The use of rice husk ash in concrete, Waste materials used in concrete manufacturing, *William Andrew Publishing/Noyes, Norwich*, 184-234, (1997)
  32. Caroling G, Sunita Kumari Tiwari, Mercy Ranjitham A and Suja R., Biosynthesis of silver nanoparticles using aqueous broccoli extract- characterization and study of antimicrobial, cytotoxic effects, *Asian Journal of Pharmaceutical and Clinical Research.*, **6**(4), 0974- 2441 (2013)
  33. Sougata Ghosh, Sumersing Patil, Mehul Ahire and Rohini Kitture., Synthesis of silver nanoparticles using *Dioscorea bulbifera* tuber extract and evaluation of its synergistic potential in combination with antimicrobial agents, *International Journal of Nanomedicine*, (2012)
  34. Ram P, Swamy V.S, Suranjit P.K and Ajit V., Biogenic synthesis of silver nanoparticles from the leaf extract of *Syzygium cumini* (L.), *International Journal of Pharma and Bio Sciences*, **3**(4), 745-752 (2012)
  35. Jae N, Saifuddin C.W, Wong A.A. and Yasumira N., *E- Journal of Chemistry.*, **6**(1), 61- 70 (2009)
  36. Thirumurugan A , Neethu Anns Tomy, Jai ganesh R and Gobikrishnan S., Biological reduction of silver nanoparticles using plant leaf extracts and its effect on increased antimicrobial activity against clinically isolated organism *Scholars Research Library*, **2**(6), 279-284 (2010)
  37. John De Britto A, Herin Sheeba Gracelin D and Benjamin Jeya Rathna Kumar P., Green synthesis of silver nano particles and their Antibacterial activity, *unique journal of pharmaceutical and biological sciences*, **2** (1), 51-55 (2014)
  38. Shiva Shankar S, Ahmad A, Pasricha R and Sastry M., *J. Mater. Chem.*, **13**, 1822 (2003)
  39. David E, Elumalai E.K, Prasad T.N.V.K.V, Venkata Kambala and Nagajyothi P.C., Green synthesis of silver nanoparticle using *Euphorbia hirta* L and their antifungal activities, *Archives of Applied Science Research.*, **2**(6), 76-81 (2010)